



HAL
open science

Effect of supercritical carbon dioxide on polystyrene extrusion

Martial Sauceau, Clémence Nikitine, Élisabeth Rodier, Jacques Fages

► **To cite this version:**

Martial Sauceau, Clémence Nikitine, Élisabeth Rodier, Jacques Fages. Effect of supercritical carbon dioxide on polystyrene extrusion. *Journal of Supercritical Fluids*, 2007, 43 (2), pp.367 - 373. 10.1016/j.supflu.2007.05.014 . hal-01829541

HAL Id: hal-01829541

<https://imt-mines-albi.hal.science/hal-01829541>

Submitted on 17 Jul 2018

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

Effect of supercritical carbon dioxide on polystyrene extrusion

M. Sauceau*, C. Nikitine, E. Rodier, J. Fages

RAPSODEE Research Centre, UMR EMAC-CNRS 2392, École des Mines d'Albi, 81013 Albi, France

Abstract

A study on the extrusion of polystyrene was carried out using supercritical carbon dioxide (scCO₂) as foaming agent. scCO₂ modifies the rheological properties of the material in the barrel of the extruder and acts as a blowing agent during the relaxation at the passage through the die. For experiments, a single-screw extruder was modified to be able to inject scCO₂ within the extruded material. The effect of operating parameters on material porosity was studied. Samples were characterized by using water-pycnometry, mercury-porosimetry and scanning electron microscopy. Polystyrene with expansion rate about 15–25% was manufactured. A rapid cooling just downstream the die is important to solidify the structure. The die temperature allows the control of the porosity structure. CO₂ concentration shows no significant influence.

Keywords: Polystyrene; Polymer; Foam; Extrusion; Supercritical carbon dioxide

1. Introduction

Extrusion is a process of converting a raw material into a product of uniform shape and density by forcing it through a die under controlled conditions [1]. Industrial applications of the extrusion process dates back to the 1930s. It is extensively applied in the plastic and rubber industries, where it is one of the most important manufacturing processes. A particular application concerns the built up of polymeric foams. Conventional foamed products are produced using either chemical or physical blowing agents. Various chemical blowing agents, which are generally low molecular weight organic compounds, are mixed into a polymer matrix and decompose when heated beyond a threshold temperature. This results in the release of a gas, and thus the apparition of bubbles. This implies however the presence of residues in material and the need for an additional stage to eliminate them. Techniques using physical agents include the mixing of a gas with melted polymer. Then, a thermodynamic instability is induced through a pressure or temperature change to nucleate bubbles of the blowing agent. After nucleation, the bubble growth is controlled by reducing the temperature below the glass transition temperature of the polymer.

A supercritical fluid (SCF) is defined as a substance for which both pressure and temperature are above the critical

value. In general, SCFs offer mass transfer advantages over conventional organic solvents because of their gas-like diffusivity, liquid-like density, low viscosity and surface tension [2]. In particular, supercritical carbon dioxide (scCO₂) has emerged as an important SCF due to its many desirable attributes such as low cost, non-toxicity, non-flammability, chemical inertia and easily accessible supercritical conditions ($T_c = 31.1\text{ }^\circ\text{C}$, $P_c = 7.38\text{ MPa}$). When CO₂ is raised above its critical point, its physicochemical properties can be continuously tuned between vapour-like and liquid-like limits by varying the system pressure and/or temperature. Moreover, scCO₂ has been widely used in polymer processing [3,4] as it is possible to dissolve large quantities of CO₂ in a variety of polymers [5,6]. This involves in particular the swelling and the plasticization of the polymer, inducing changes in mechanical and physical properties [3]. For instance, scCO₂ decreases the glass transition temperature, the interfacial tension or the viscosity of various polymers, without changing the viscoelastic behaviour [7]. With polystyrene (PS), the glass transition temperature decreases from 105 °C to 98 °C and to 46.4 °C with a CO₂ mass fraction of 1 and 5.9%, respectively [8] and the interfacial tension decreases linearly from 28 to 17 mJ m⁻² on a CO₂ pressure range from 1 to 10 MPa at 200 °C [9,10].

The presence of scCO₂ in extrusion process modifies rheological properties of the polymer in the barrel of the extruder and acts as a blowing agent during the relaxation at the passage through the die. Thus, its high solubilization in the polymer results in extensive expansion at the die. The reduction of

* Corresponding author. Tel.: +33 5 63 49 33 18; fax: +33 5 63 49 32 43.
E-mail address: martial.sauceau@enstimac.fr (M. Sauceau).

viscosity decreases the mechanical constraints and the operating temperature within the extruder.

In classical theory, the homogeneous nucleation rate (i.e. the number of cells created per units of time and volume) can be expressed as a function of the Gibbs free energy barrier for the formation of a critical bubble nucleus and temperature [11]. The theory suggests that the energy barrier and the interfacial tension decrease as the supersaturation pressure increases. Consequently, the homogeneous nucleation rate increases and a large number of small cells is obtained. In fact, controlling supercritical CO₂ quantity allows the modification of the cell density and the cell size in microcellular foaming.

The objective of this work is to develop a process of extrusion coupled with the use of scCO₂. In a preliminary work, an extruder was modified in order to be able to inject scCO₂ within the extruded material and some experiments were performed on polystyrene (PS) [12]. A pressure decrease within the extruder was observed upon CO₂ injection and samples of porous PS were obtained, with a decrease of their apparent density from 30 to 40%. However, the porous structure was irregular, with bubble diameters varying from 100 μm to 1 mm. This could be explained considering the quality of the mixture in the extruder. Indeed, an insufficient homogeneity of mixture PS–CO₂ could explain the irregularity of porosity. Therefore, the experimental device has been modified in order to improve the mixture between the two components. In this work, this novel device has been tested with PS and the influence of cooling, die temperature and CO₂ content on the material properties has been studied.

2. Experimental

2.1. Materials and equipment

Polystyrene (choc, BP Chemicals) was used in experiments and CO₂ (N45, Air Liquide) was applied as the physical foaming agent.

Fig. 1 shows the flow diagram of the foaming system. The extruder used in this study is a single-screw machine with a 20 mm screw diameter and a length to diameter ratio (L/D) of 20 (Rhéoscam, SCAMEX). Carbon dioxide is pumped from a cylinder by a syringe pump (260D, ISCO), which allows the delivery of small flow rates (i.e. 0.1 μl min⁻¹). The pump is run in constant volumetric flow rate mode and CO₂ is introduced at the same pressure as the pressure prevailing in the extruder. The injection position is located at about 12D from hopper, in a zone where the screw diameter is constant. A checking valve is inserted in the line to prevent pollution of CO₂. The polymer–CO₂ mixture is then passed through a mixer (type ‘pineapple’, composed of diamond spike). This element, inserted before the die, provides a dynamic distributive mixing between the two components [13]. The pressure drop through the die can be adjusted by modifying restriction opening by means of a screw placed in the polymer flow.

The pressure, the temperature and the volumetric CO₂ flow rate are measured within the syringe pump. CO₂ density is obtained by Peng Robinson’s equation of state [14]. In operating conditions used, CO₂ concentration is always smaller than saturation concentration. Consequently, polystyrene–CO₂ blend is in a single phase at thermodynamic equilibrium [15,16].

The temperature inside the barrel is regulated at four locations: T_1 , T_2 before and after the CO₂ injection, T_3 before the mixing element and T_4 before the die. Only the temperature of the die T_4 is changed at each experiment. Three other temperatures and screw speed are kept constant at 180 °C and 50 rpm, respectively. At each new condition, temperature T_{mat} and pressure P_{mat} of material are measured just before entry within the die. The flow rate of polymer Q_{mat} , of the order of 0.6 kg h⁻¹, is obtained by weighing the extrudate at the end of the experiment. CO₂ concentration C_{CO_2} in the polystyrene can thus be expressed as weight flow rate ratio.

A large decrease of the pressure into the extruded matter was observed when scCO₂ was injected, mainly due to the decrease of melt viscosity [17]. For all experiments, 3–5 mm outer

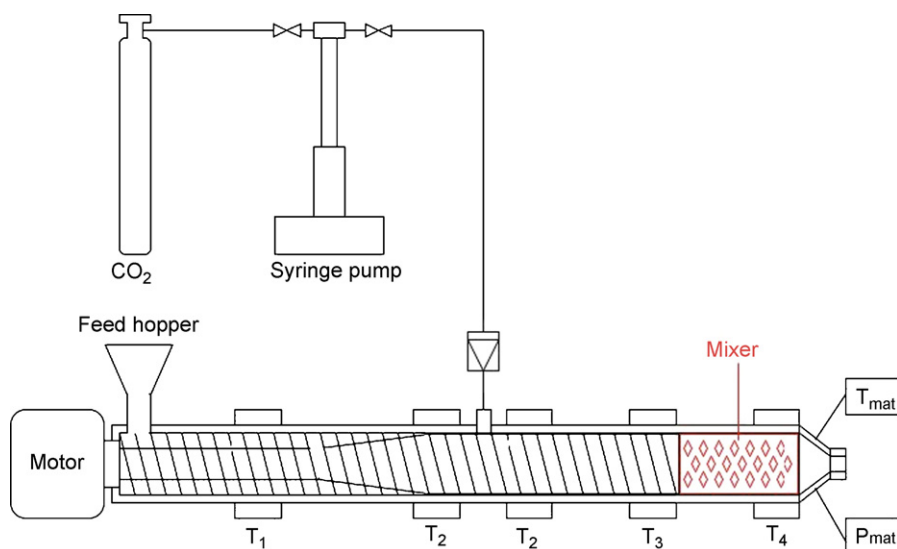


Fig. 1. Flow diagram of the extruder.

diameter PS cylinders were obtained. Once stable conditions have been established, samples were collected and submitted to two kinds of cooling. The first one consists in leaving the polymer at ambient conditions at about 22 °C. In the second one, material is plunged into a water bath at ambient temperature immediately after its exit from the die.

To study the influence of operating parameters on porous structure, several experiments have been carried out at 12 MPa varying cooling mode, die temperature and CO₂ concentration, other parameters being constant. Experiments are time and material consuming and we have thus chosen to study die temperature and CO₂ content at three levels to observe the main tendencies of the influence of these operating parameters.

2.2. Characterization

Porosity ε is defined as the ratio of void volume to the total volume of the sample and can be calculated by the following

equation:

$$\varepsilon = \frac{V_e}{V_t} = 1 - \frac{V_m}{V_t} \quad \text{with } V_t = V_e + V_m \quad (1)$$

where V_t is the total volume of the sample, V_e the void volume and V_m is the solid volume. Two methods are used to characterize porosity: the water-pycnometry and the Hg-porosimetry (Autopore III, Micromeritics).

The water-pycnometry allows the measurement of the apparent density ρ_{app} of expanded samples and thus to calculate the total porosity ε :

$$\varepsilon = 1 - \frac{\rho_{app}}{\rho_{PS}} \quad (2)$$

where ρ_{ps} is the bulk density of raw polystyrene, which corresponds to polystyrene extruded without CO₂ injection. This density, also measured by water-pycnometry, is equal to 1 g cm⁻³.

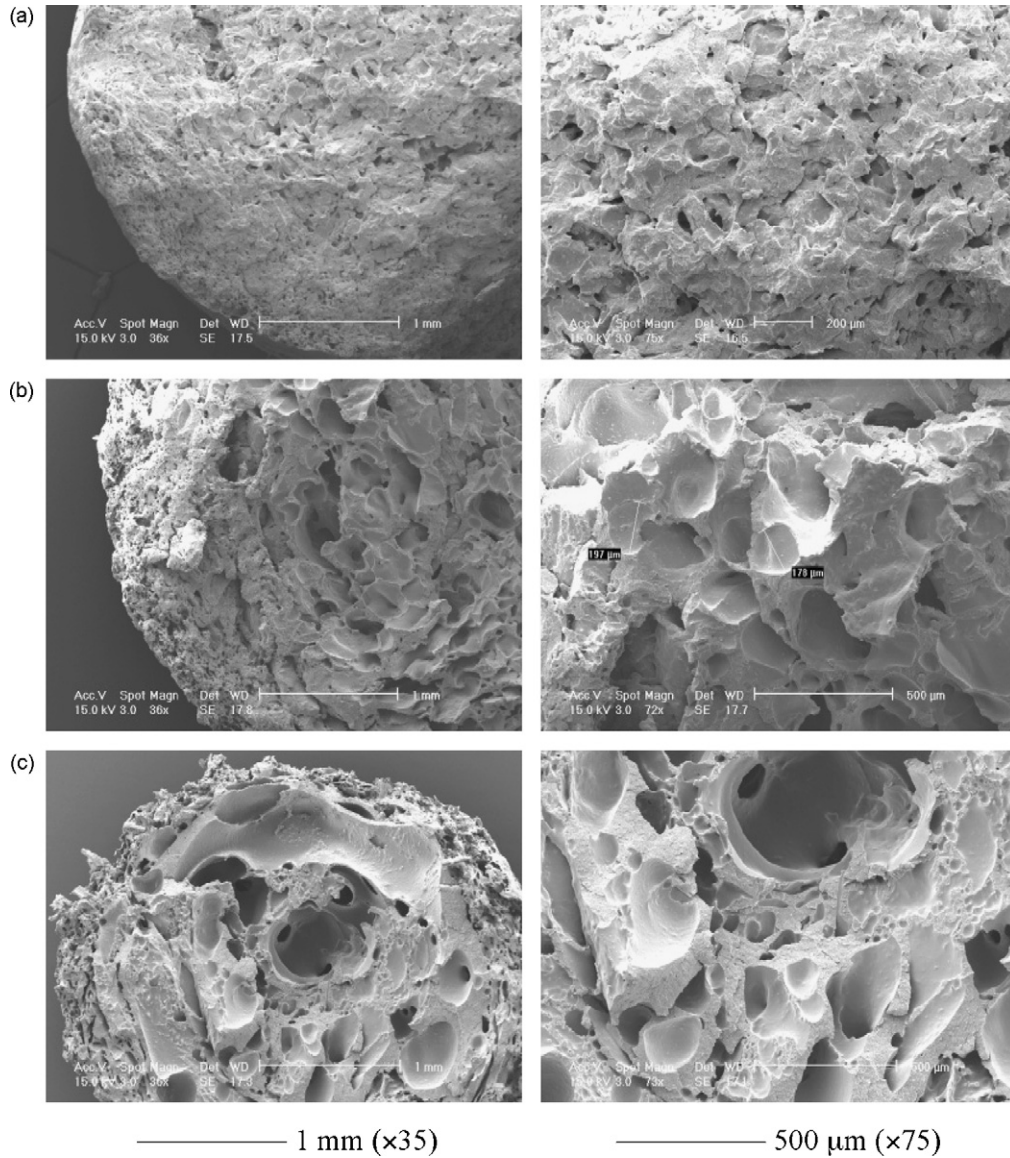


Fig. 2. SEM pictures of samples cooled in air processed at $P_{mat} = (12 \pm 1)$ MPa, $C_{CO_2} = (5 \pm 0.2)\%$ and (a) $T_{mat} = 175$ °C; (b) $T_{mat} = 185$ °C; (c) $T_{mat} = 200$ °C.

In Hg-porosimetry, mercury is used as penetrating fluid in a calibrated pycnometer. It is forced to enter into the pores by means of an increasing pressure related to the diameter of the filled pore. Each pressure level required to fill the sample provides the diameter D_p and the volume V_p of corresponding pores. In this method, only the opened porosity ε_{eff} is filled by mercury and can thus be calculated with the following equation:

$$\varepsilon_{\text{eff}} = \frac{\sum V_p}{V_t} \quad (3)$$

To quantify the fraction of the total porosity which is opened, an open porosity rate X_{eff} can be defined as the ratio of the opened porosity to the total porosity:

$$X_{\text{eff}} = \frac{\varepsilon_{\text{eff}}}{\varepsilon} \quad (4)$$

It has to be noted that a minimal pressure is required to begin a measurement in Hg-porosimetry. This lowest usable pressure corresponds to a maximal value of pore diameter equal to about 200 μm .

To complete the characterization of the porosity structure, samples were examined by scanning electron microscopy (XL30 ESEM, FEG, Philips).

3. Results and discussion

3.1. Influence of the cooling mode

Fig. 2 compares three PS samples processed at different die temperatures. All of them have an external skin with a roughly constant thickness. It is probably formed by an effect of hardening during the cooling. The differences appear in the centre of the cylinders. Indeed, with increasing temperature, pores become larger and more irregular. Finally, for highest temperatures, large pores occupy all the central part. This effect is more important in the rod centre, which is more slowly cooled. Moreover, at lower temperature, the porous structure is improved by the addition of the mixer [12].

Table 1 shows the evolution of porosity ε as a function of temperature. An important increase of ε occurs from 175 to 185 $^{\circ}\text{C}$, probably due to growth of the pores which conserve a

Table 1

Porosity ε at different temperatures T_{mat} of samples processed at $P_{\text{mat}} = (12 \pm 1)$ MPa, $C_{\text{CO}_2} = (5 \pm 0.2)\%$ and cooling in air

| T_{mat} ($^{\circ}\text{C}$) | ε (%) |
|---|-------------------|
| 175 | 16 |
| 185 | 31 |
| 200 | 30 |

regular shape. Then, porosity ε remains constant from 185 to 200 $^{\circ}\text{C}$. It seems that growth is attenuated and that coalescence phenomena are at the origin of the structure observed at 200 $^{\circ}\text{C}$.

Fig. 3 compares two samples processed in the same operating conditions but cooled by using the two different ways previously described. At this temperature, the influence of the cooling is obvious: the cooling in water allows smaller and homogeneous pores and a porosity reduced from 30 to 19%. Growth and coalescence are attenuated and it is thus important to solidify rapidly the structure to carry out relevant observations on the influence of operating parameters.

3.2. Effect of die temperature

Fig. 4 shows SEM pictures of samples obtained at different die temperatures. Increasing the temperature increases the pore size and decreases the pore number. It appears a radial distribution of pore size, with larger pores in the cylinder centre. The shape evolves also with temperature, the pores becoming more regular and finally almost spherical at 220 $^{\circ}\text{C}$.

Arora et al. [18] have used a batch process to foam PS by using CO_2 between 40 and 120 $^{\circ}\text{C}$. They have also observed fewer and larger pores at higher temperatures. This can be explained by the decrease of the viscosity of the substrate material causing the restrictive force restricting cell growth to decrease and the increase of the diffusivity of CO_2 within the substrate. With a continuous process, Park et al. [19] have shown that the improvement of pore structure is obtained at the price of the decrease of expansion. They have thus observed an increase of cell coalescence with increasing die temperature. More recently using also a continuous process, Han et al. [20] have done the same observation, with however coupled effects of pressure and temperature.

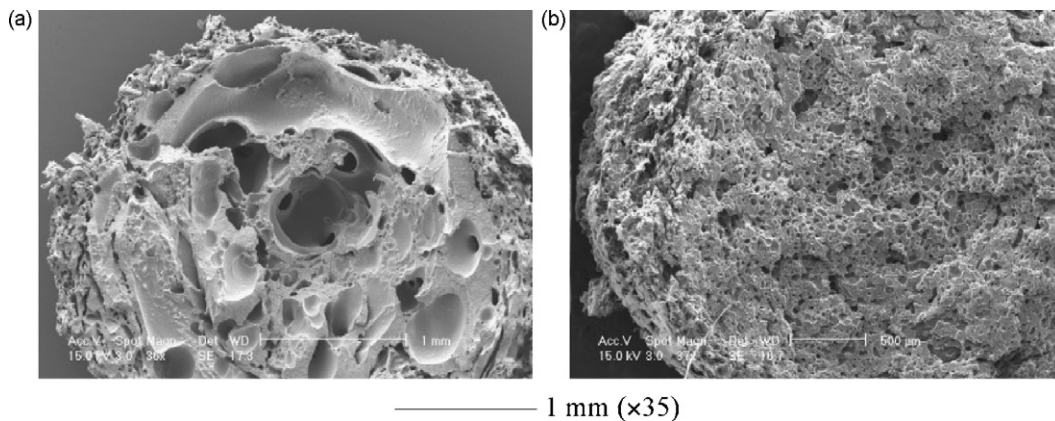


Fig. 3. SEM pictures of samples processed at $P_{\text{mat}} = (12 \pm 1)$ MPa, $T_{\text{mat}} = 200$ $^{\circ}\text{C}$, $C_{\text{CO}_2} = (5 \pm 0.2)\%$ and cooled (a) in air; (b) in water.

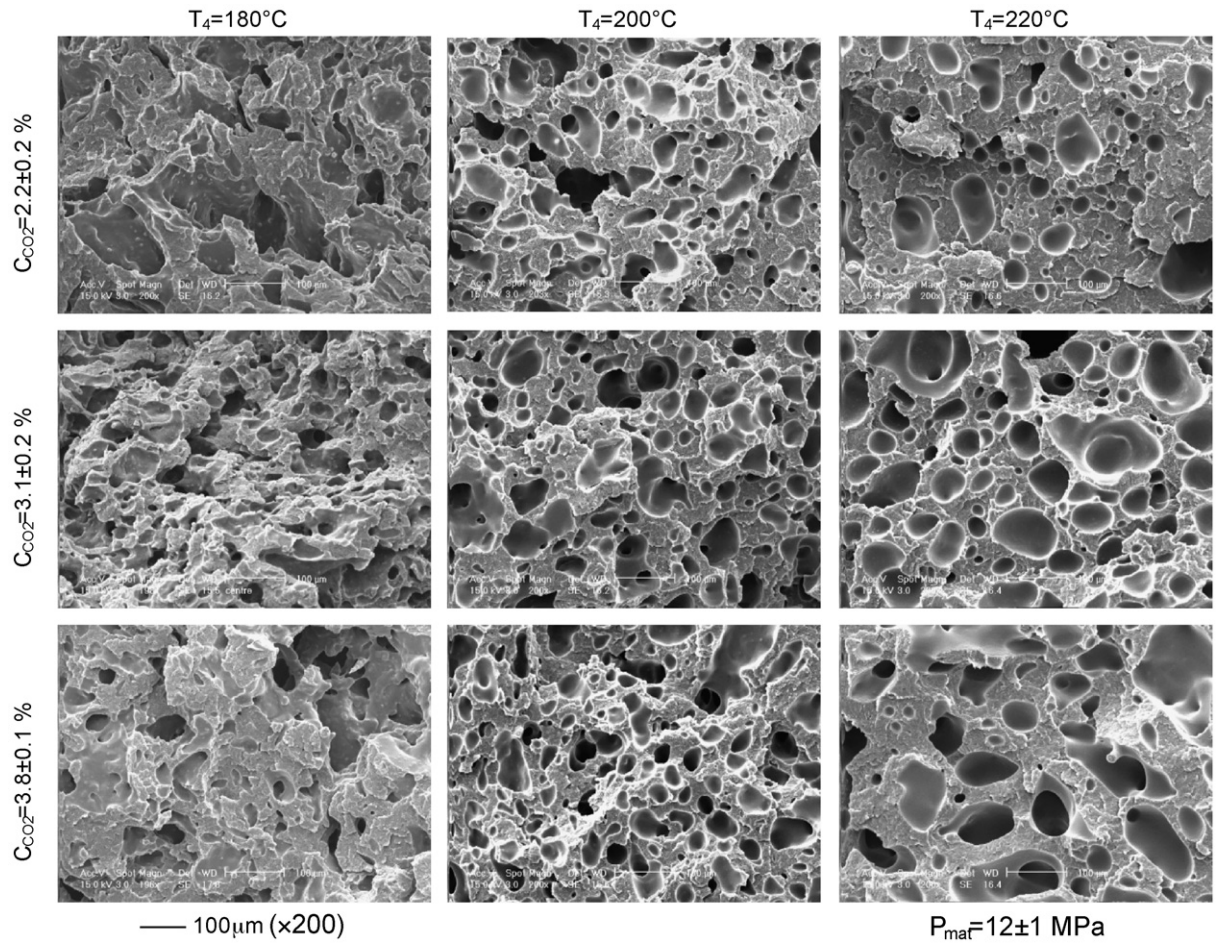


Fig. 4. SEM pictures of samples cooled in water processed at $P_{mat} = (12 \pm 1)$ MPa.

Indeed, the authors have worked with constant die geometry and, a temperature decrease has involved a pressure drop increase because of the viscosity increase, which may also influence the structure.

The relationship between die temperature and homogenous nucleation rate is complex because many physical properties depend on this temperature. Indeed, by using classical theory, it can be shown that increasing the temperature enhances the homogenous nucleation rate [20]. Thus, as previously observed in the case of air cooling, it seems that the observed evolution cannot be explained by nucleation theory but rather by an increase in the growth and coalescence phenomena, involving fewer and larger pores [18].

Fig. 5 shows the evolution of porosity with temperature. At higher CO_2 concentration, total porosity ε increases from 180 to 200 °C and then remains almost constant from 200 to 220 °C. At the lowest CO_2 concentration, the temperature exhibits no more influence on porosity. At the same time, opened porosity ε_{eff} decreases slowly with increasing temperature (Fig. 6). This leads to the decrease of the opened porosity rate ε_{eff} from 68% at 180 °C to 37% at 220 °C (Fig. 7). Growth is therefore the predominant effect at lower temperatures, while cell coalescence occurs at higher temperatures, involving the closing of these cells.

The pore size distribution obtained by Hg-porosimetry is represented at different temperatures on Figs. 8 and 9. At 180 °C, diameter of pores is between 5 and 20 μm . When the temperature increases, pore size increases to values higher than 200 μm , which is the limit of the apparatus. This evolution confirms the former conclusion that coalescence and growth phenomena occur when temperature increase and lead to larger porosity.

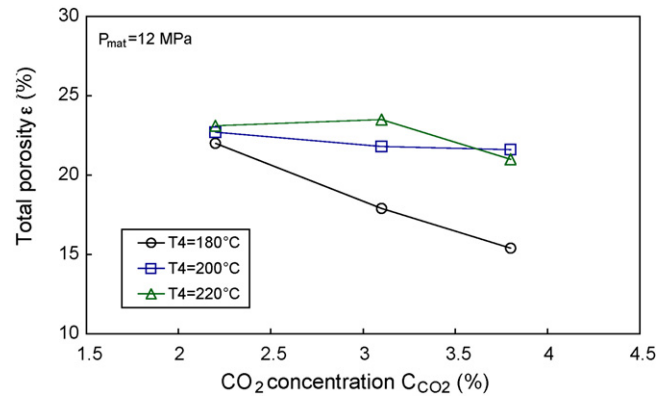


Fig. 5. Total porosity ε as function of CO_2 concentration at different temperatures.

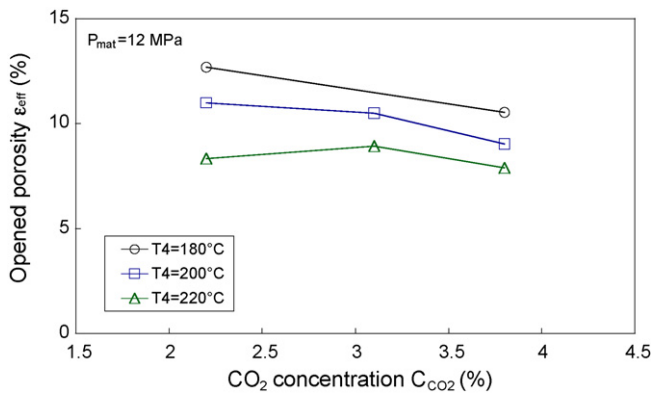


Fig. 6. Opened porosity ε_{eff} as function of CO_2 concentration at different temperatures.

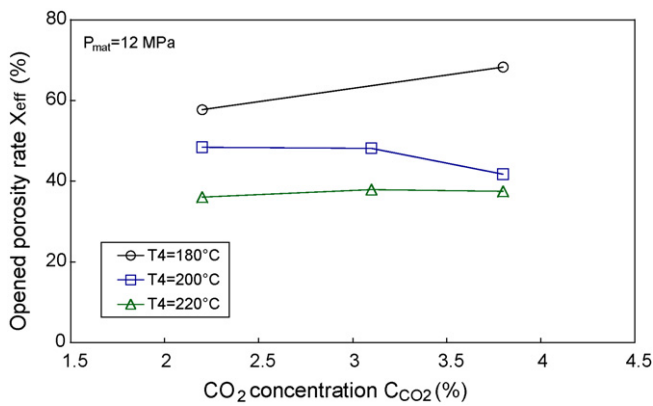


Fig. 7. Opened porosity rate X_{eff} as function of CO_2 concentration at different temperatures.

3.3. Effect of CO_2 weight ratio

On SEM pictures, the effect of CO_2 concentration is less obvious than that of the die temperature (Fig. 4). On Figs. 5 and 6, it can be seen that total porosity ε and opened porosity ε_{eff} decrease slightly with increasing CO_2 concentration, with however a higher effect at lower temperature. This finally leads to an opened porosity rate ε_{eff} almost constant (Fig. 7). Pore size distributions obtained by Hg-porosimetry confirm the lim-

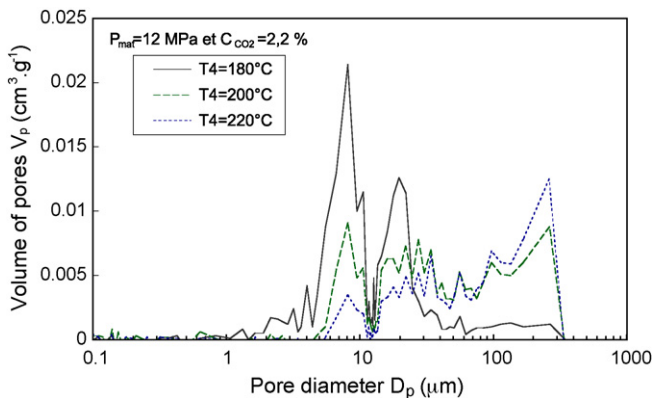


Fig. 8. Pore size distribution with 2.2% of CO_2 at different temperatures.

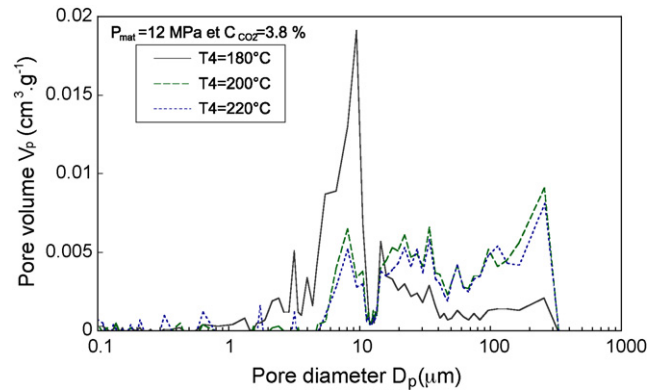


Fig. 9. Pore size distribution with 3.8% of CO_2 at different temperatures.

ited influence of CO_2 concentration, as for instance at 200 °C (Fig. 10).

It is clear that increasing CO_2 concentration increases nucleation rate [20]. However, CO_2 concentration increase involves also the modification of other key physical variables, such as for instance properties like viscosity or surface tension [7–10]. This difficulty is well illustrated by Han et al. [21] who have also studied the effect of CO_2 concentration. By means of a computational fluid dynamics program, these authors have represented profiles of pressure and saturation CO_2 fraction along the nozzle. Because of their constant die geometry, the increase of CO_2 concentration was coupled with a pressure decrease. They have then found that the more CO_2 in the melt, the earlier the bubbles begin to nucleate and grow. In other words, a high CO_2 content gives more nuclei, but a longer time for bubble growth. However, during their experiments, it was noted that both the pressure and the pressure drop rate are independent of CO_2 content. Finally, they observed that, at low CO_2 concentrations, cell size decreases and cell density increases with increasing CO_2 content. While at high CO_2 concentrations (above 4%), cell size tends to be independent of CO_2 content, probably because of extra gas, which is not used to nucleate cells. If we translate these experimental observations in terms of total porosity, no clear trend appears. Indeed, cell size increase and cell density decrease show opposite effects on total porosity.

In this work, no significant influence of CO_2 concentration has been observed. However, PS- CO_2 blend is theoretically in a

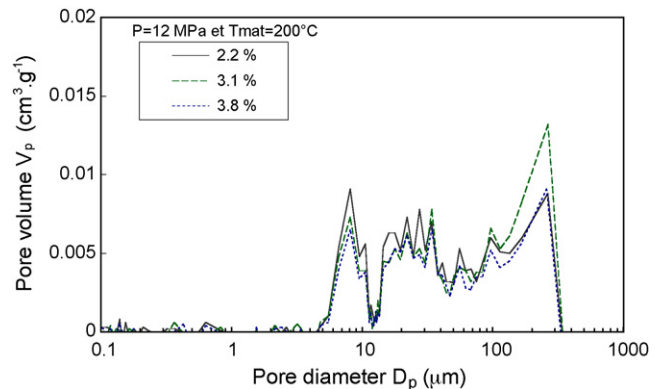


Fig. 10. Pore size distribution at 200 °C and different CO_2 concentrations.

single phase at thermodynamic equilibrium, as CO₂ weight solubility was estimated to be at about 5% at 180 °C and 12 MPa [15]. Thus, as observed by Han et al. [21], it seems that a part of injected CO₂ remains as extra gas and is not used to nucleate cells. Furthermore, higher CO₂ content than studied range usually causes unstable polymer flow with oscillating pressure, what would tend to confirm this assumption.

4. Conclusion

A process based on extrusion coupled with the use of supercritical carbon dioxide (scCO₂) was implemented. scCO₂ modifies the rheological properties of the material in the barrel of the extruder and acts as a blowing agent during the relaxation at the passage through the die. A novel experimental device based on a single-screw extruder was developed. It allows the injection of scCO₂ into extruded melt, the mixing of both compounds and the creation of porosity into the extruded polymer. In this work, it was applied to polystyrene (PS). Operating temperatures and mechanical constraints within the extruded material were reduced by the injection of CO₂. The effects of cooling mode, die temperature and CO₂ concentration on material porosity were studied. PS with porosity from 15 to 25% was manufactured. A rapid cooling is important to solidify the structure. Increasing die temperature increases growth and coalescence phenomena, and thus increases total porosity and pore diameter. Finally, this parameter allows the control of the porosity structure. CO₂ concentration shows no significant influence. It was explained by the fact that a part of injected CO₂ remains as extra gas and is not used to nucleate cells.

References

- [1] C. Rauwendaal, *Polymer Extrusion*, Hanser Publishers, München, 2001.
- [2] C. Eckert, B. Knutson, P. Debenedetti, Supercritical fluids as solvents for chemical and materials processing, *Nature* 383 (1996) 313–383.
- [3] S.G. Kazarian, Polymer processing with supercritical fluids, *Polym. Sci. Ser. C* 42 (2000) 78–101.
- [4] S.P. Nalawade, F. Picchioni, L.P.B.M. Janssen, Supercritical carbon dioxide as a green solvent for processing polymer melts: processing aspects and applications, *Prog. Polym. Sci.* 31 (2006) 19–43.
- [5] J.H. Aubert, Solubility of carbon dioxide in polymers by the quartz crystal microbalance technique, *J. Supercrit. Fluids* 11 (1998) 163–172.
- [6] Y. Sato, K. Fujiwara, T. Takikawa, S. Takishima, H. Masuoka, Solubilities and diffusion coefficients of carbon dioxide and nitrogen in polypropylene, high-density polyethylene, and polystyrene under high pressures and temperatures, *Fluid Phase Equilib.* 162 (1999) 261–276.
- [7] D. Gourgouillon, H.M.N.T. Avelino, J.M.N.A. Fareleira, M. Nunes Da Ponte, Simultaneous viscosity and density measurement of supercritical CO₂-saturated PEG 400, *J. Supercrit. Fluids* 13 (1998) 177–185.
- [8] P.D. Condo, I.C. Sanchez, C.G. Panayiotou, K.P. Johnston, Glass transition behavior including retrograde vitrification of polymers with compressed fluid diluents, *Macromolecules* 25 (1992) 6119–6127.
- [9] H. Li, L.J. Lee, D.L. Tomasko, Effect of carbon dioxide on the interfacial tension of polymer melts, *Ind. Eng. Chem. Res.* 43 (2004) 509–514.
- [10] H. Park, C.B. Park, C. Tzoganakis, K.H. Tan, P. Chen, Surface tension measurement of polystyrene melts in supercritical carbon dioxide, *Ind. Eng. Chem. Res.* 45 (2006) 1650–1658.
- [11] J.H. Han, C.D. Han, Bubble nucleation in polymeric liquids. II. Theoretical considerations, *J. Polym. Sci. Part B* 28 (1990) 743–761.
- [12] M. Sauceau, S. Puissant, D. Richon, J. Fages, Développement de procédés d'extrusion assistés par un fluide supercritique, in: *Groupe Français de Rhéologie (Ed.), Proceedings of the 39th Colloque du Groupe Français de Rhéologie*, 2004, p. 248.
- [13] B. Vergnes, S. Puissant, Extrusion monovis (partie 1), *Techniques de l'Ingénieur traité Plastiques et Composites AM 3 650* (2002) 1–16.
- [14] D.-Y. Peng, D. Robinson, A new two-constant equation of state, *Ind. Eng. Chem. Fundam.* 15 (1976) 59–64.
- [15] Y. Sato, M. Yurugi, K. Fujiwara, S. Takishima, H. Masuoka, Solubilities of carbon dioxide and nitrogen in polystyrene under high temperature and pressure, *Fluid Phase Equilib.* 125 (1996) 129–138.
- [16] Y. Sato, T. Takikawa, S. Takishima, H. Masuoka, Solubilities and diffusion coefficients of carbon dioxide in poly(vinyl acetate) and polystyrene, *J. Supercrit. Fluids* 19 (2001) 187–198.
- [17] C. Kwag, C.W. Manke, E. Gulari, Rheology of molten polystyrene with dissolved supercritical and near-critical gases, *J. Polym. Sci. Part B* 37 (1999) 2771–2781.
- [18] K.A. Arora, A.J. Lesser, T.J. McCarthy, Preparation and characterization of microcellular polystyrene foams processed in supercritical carbon dioxide, *Macromolecules* 31 (1998) 4614–4620.
- [19] C.B. Park, A.H. Behraves, R.D. Venter, Low density microcellular foam processing in extrusion using CO₂, *Polym. Eng. Sci.* 38 (1998) 1812–1823.
- [20] X. Han, K.W. Koelling, D.L. Tomasko, L.J. Lee, Effect of die temperature on the morphology of microcellular foams, *Polym. Eng. Sci.* 43 (2003) 1206–1220.
- [21] X. Han, K.W. Koelling, D.L. Tomasko, L.J. Lee, Continuous microcellular polystyrene foam extrusion with supercritical CO₂, *Polym. Eng. Sci.* 42 (2002) 2094–2106.